

---

---

**Steel — Hardenability test by end  
quenching (Jominy test)**

*Acier — Essai de trempabilité par trempé en bout (essai Jominy)*

STANDARDSISO.COM : Click to view the full PDF of ISO 642:1999



<b>Contents</b>	<b>Page</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Principle</b> .....	<b>1</b>
<b>4 Symbols and designations</b> .....	<b>2</b>
<b>5 Form of test pieces and their preparation</b> .....	<b>2</b>
<b>6 Apparatus</b> .....	<b>3</b>
<b>7 Heating and quenching of test piece</b> .....	<b>6</b>
<b>8 Preparation for, and measurement of, hardness after quenching</b> .....	<b>6</b>
<b>9 Expression of results</b> .....	<b>7</b>
<b>10 Test report</b> .....	<b>8</b>
<b>Annex A (informative) Specification for the hardenability of a product</b> .....	<b>10</b>
<b>Annex B (informative) Additional information to clause 10</b> .....	<b>13</b>
<b>Annex C (informative) Calculation of the hardenability</b> .....	<b>15</b>
<b>Bibliography</b> .....	<b>16</b>

STANDARDSISO.COM : Click to view the full PDF of ISO 642:1999

© ISO 1999

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization  
Case postale 56 • CH-1211 Genève 20 • Switzerland  
Internet iso@iso.ch

Printed in Switzerland

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 642 was prepared by Technical Committee ISO /TC 17 *Steel*, Subcommittee SC 7, *Methods of testing (other than mechanical tests and chemical analysis)*.

This second edition cancels and replaces the first edition (ISO 642:1979) which has been technically revised.

Annexes A, B, and C of this International Standard are for information only.

STANDARDSISO.COM : Click to view the full PDF of ISO 642:1999



# Steel — Hardenability test by end quenching (Jominy test)

## 1 Scope

This International Standard specifies a method for determining the hardenability of steel by end quenching (Jominy test) by using a test piece 25 mm in diameter and 100 mm long.

NOTE By agreement and for a defined field of application, the test described in this International Standard may be replaced by the calculation of the Jominy curve in accordance with an accepted mathematical model (see annex C). In case of dispute, the test shall be carried out.

## 2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this International Standard. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 6507-1, *Metallic materials — Vickers hardness test — Part 1: Test method*.

ISO 6508-1, *Metallic materials — Rockwell hardness test — Part 1: Test method (scales A, B, C, D, E, F, G, H, K, N, T)*.

ISO 6508-2, *Metallic materials — Rockwell hardness test) — Part 2: Verification and calibration of testing machines (scales A, B, C, D, E, F, G, H, K, N, T)*.

ISO 6508-3, *Metallic materials — Rockwell hardness test — Part 3: Calibration of reference blocks (scales A, B, C, D, E, F, G, H, K, N, T)*.

## 3 Principle

The test consists of:

- a) heating a cylindrical test piece to a specified temperature in the austenitic range for a specified period of time;
- b) quenching it by spraying water on one of its ends under specified conditions;
- c) measuring the hardness at certain given points, on longitudinal flats made on the test piece, in order to determine the hardenability of the steel by variations of this hardness.

## 4 Symbols and designations

Symbol	Designation	Value
$L$	Total length of test piece	$(100 \pm 0,5)$ mm
$D$	Diameter of test piece	$(25^{+0,5}_0)$ mm
$t$	Time during which test piece is maintained at heating temperature	$(30^{+5}_0)$ min
$t_m$	Maximum time lag between removal of test piece from furnace and start of quenching	5 s
$T$	Temperature of cooling water	$(20 \pm 5)$ °C
$a$	Internal diameter of vertical water supply pipe	$(12,5 \pm 0,5)$ mm
$h$	Height of water jet without test piece in position	$(65 \pm 10)$ mm
$l$	Distance from end of water supply pipe to lower end of test piece	$(12,5 \pm 0,5)$ mm
$e$	Depth of flats for measurement of hardness	$(0,4 \text{ to } 0,5)$ mm
$d$	Distance, in millimetres, from quenched end to points where hardness is measured	
$J_{xx-d}$	Jominy hardenability index at distance $d$ , in Rockwell HRC-mm	
$JHV_{xx-d}$	Jominy hardenability index at distance $d$ , in Vickers HV 30-mm	

## 5 Form of test pieces and their preparation

### 5.1 Sampling

In the absence of specific requirements in the product standard, and unless otherwise agreed on the order and regardless of the thickness (or diameter) of the product, the sampling of test piece from the product can be made:

- either by hot rolling or forging of test piece with 30 mm to 32 mm diameter;
- or by machining of test piece with diameter  $(25^{+0,5}_0)$  mm whose axis shall be at least at  $(20^{+5}_0)$  mm from the surface product (see Figure 1).

In case of products from continuous casting, a minimum reduction ratio 8:1 is recommended before sampling.

In all the forming processes preceding the machining of the test piece, the deformation of the product from all sides should be as uniform as possible.

In the case of a separately cast reference test piece, the original cross section before deformation must be at least three times that corresponding to the required diameter of 30 mm to 32 mm.

By special agreement, the test piece can be obtained by a suitable casting process and tested in the as-cast condition.

The flats of the test piece shall have their axes at approximately the same distance from the product surface (see Figure 1). For this purpose, the test piece shall be marked so that its position in the round bar can be clearly recognized.

## 5.2 Dimensions

**5.2.1** The test piece shall consist of a round bar machined to a diameter of 25 mm and a length of 100 mm.

**5.2.2** The end of the test piece which will not be quenched shall be 30 mm to 32 mm or 25 mm in diameter, depending upon the form of that end. Two examples, test pieces with a flange or an undercut (to permit rapid centring and fitting in position for the quenching operation by means of an appropriate support) are shown in Figure 2.

**5.2.3** The test piece shall, if necessary, be marked (on the end opposite to the end to be quenched) to enable its position to be identified in relation to the original product.

## 5.3 Heat treatment

Unless otherwise agreed, the test piece shall be normalized before machining and quenching. The normalizing process shall be carried out at the average temperature within the range specified in the material standard. If the material standard does not specify a temperature for normalizing, the normalizing temperature shall be subject to special agreement or duly selected by the testing department. The holding time at normalizing temperature shall be  $(30^{+5}_0)$  min.

The heat treatment shall be carried out in each case in such a way that the finish-machined test piece shows absolutely no traces of decarburization.

## 5.4 Machining

The cylindrical surface of the test piece shall be machined by fine turning; the surface of the test piece end to be quenched shall have a reasonably fine finish, preferably obtained by fine grinding, and should be free from burrs (see Figure 2).

## 6 Apparatus

The apparatus consists of a device for quenching the test piece.

**6.1** The quenching device consists essentially of a means of suddenly inducing the water jet to impinge on the end of the test piece to be quenched. This can be realized e.g., by a quick action tap and a system to adjust the flow rate of the water or a disc allowing the water jet to be released and cut off rapidly (see Figure 3). In the case of a quick action tap the length of the water supply pipe behind the tap shall be at least 50 mm in order to ensure non-turbulent water flow.

**6.2** The relative positions of the end of the water supply pipe and the test piece support shall be such that the distance between the end of the water supply pipe and the test piece end to be quenched is  $(12,5 \pm 0,5)$  mm (see Figure 3).

**6.3** The test piece support shall allow precise centring of the test piece above the end of the water supply pipe and the holding of it in position during spraying. It shall be dry while the test piece is being placed in position; the test piece shall be protected from water splashes while it is being placed in position as well as before and during the actual end quenching operation.


**6.4** The height of the water jet above the end of the water supply pipe without the test piece in position shall be  $(65 \pm 10)$  mm (see Figure 4).

The water temperature in the pipe shall be  $(20 \pm 5)$  °C.

In the case of comparative tests, tests shall be carried out with the same water temperature.

**6.5** The test piece shall be protected from draughts throughout the heating and quenching.


Dimensions in millimetres

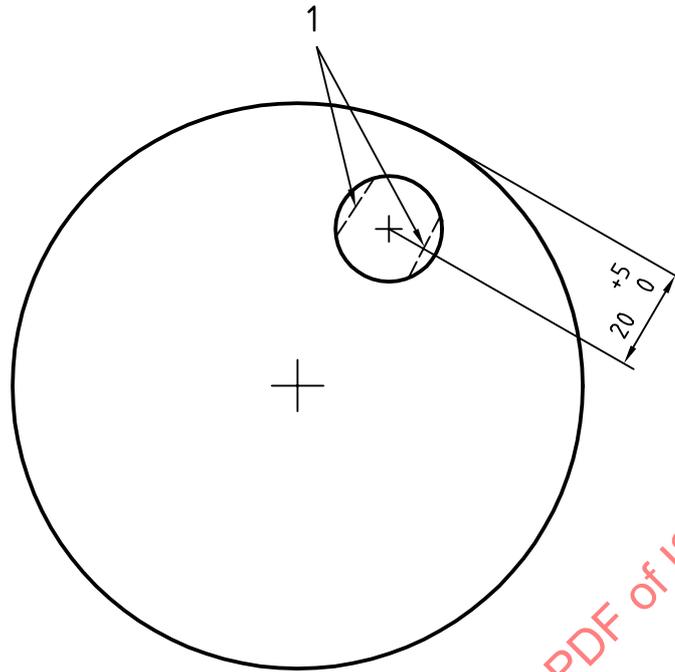

**Key**  
1 Test flats.

Figure 1 — Sampling by machining of the test piece

Dimensions in millimetres

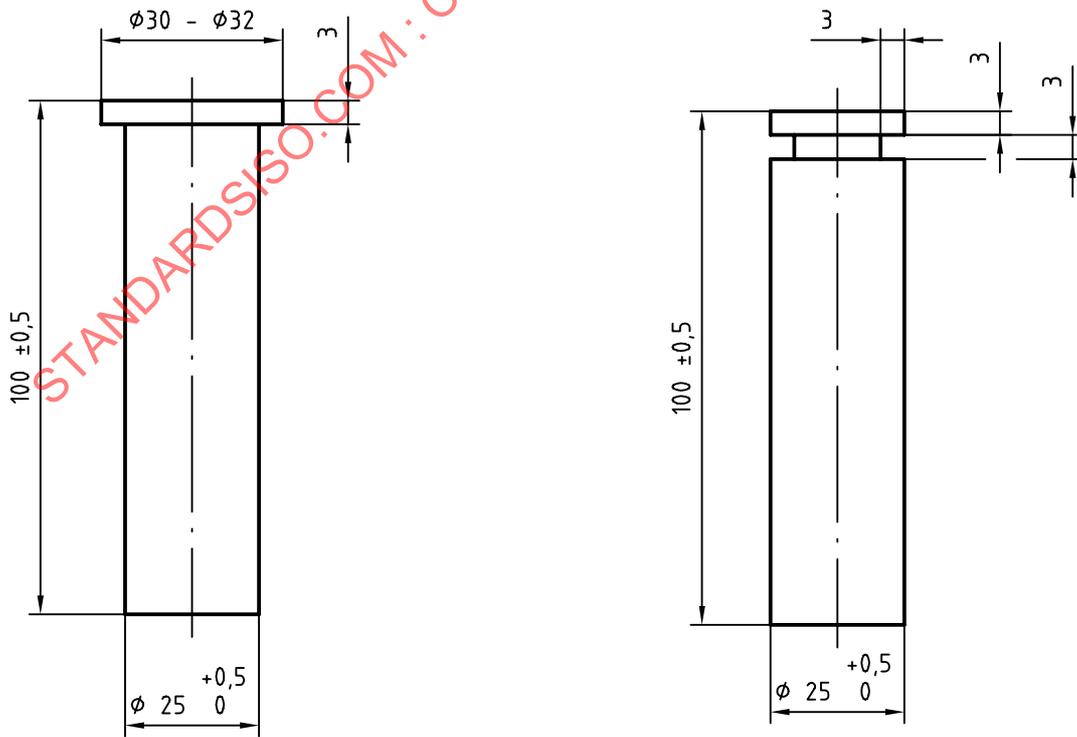


a) test piece with flange

b) test piece with undercut

Figure 2 — Dimensions of test piece


Dimensions in millimetres

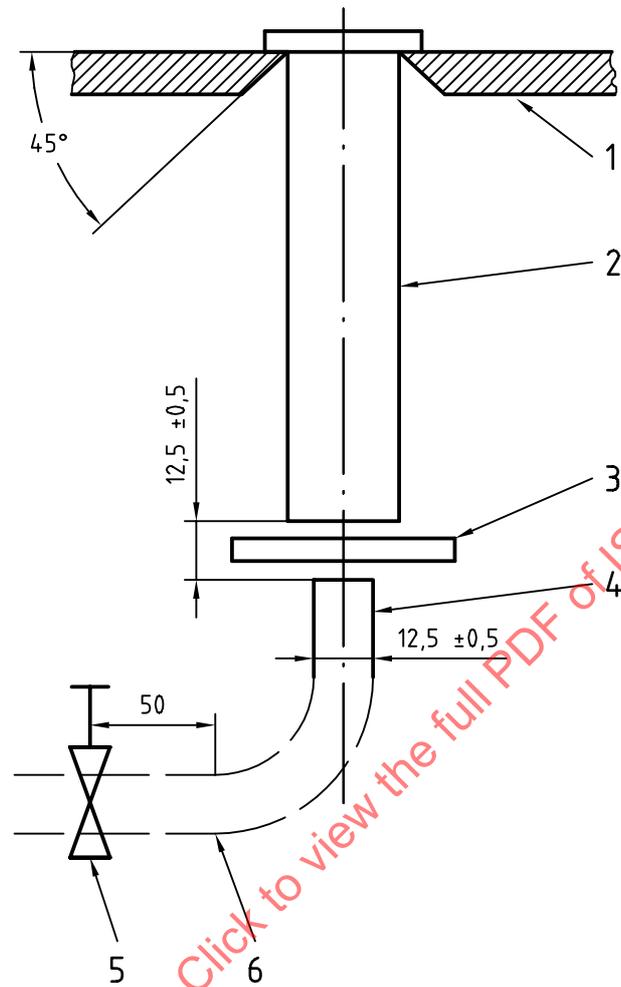**Key**

- |  |                             |
|--|-----------------------------|
| 1 Device for fixing and centring the test piece. | 4 End of water supply pipe. |
| 2 Test piece in position.                        | 5 Quick-action tap.         |
| 3 Disc.  | 6 Water supply pipe.        |

**Figure 3 — Diagram of quenching device**

Dimensions in millimetres

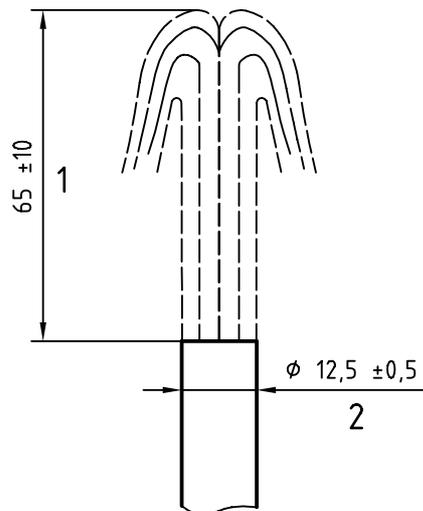**Key**

- 1 Height of free water jet.
- 2 Diameter of end of water supply pipe.

**Figure 4 — End of water supply pipe****7 Heating and quenching of test piece****7.1 Heating**

**7.1.1** The test piece shall be heated uniformly to the temperature specified in the relevant product standard or fixed by special agreement for at least 20 min and then maintained for  $(30^{+5}_0)$  min at the agreed-upon temperature. For particular types of furnace, this period can be determined as a result of previous experience establishing the minimum time necessary for the centre of the test piece to reach the desired temperature (this temperature can be verified by means of, e.g., a thermocouple placed in a hole drilled along the axis of the test piece at the head end).

**7.1.2** Precautions shall be taken to minimize decarburization or carburization of the test piece, and to avoid any marked oxidation with formation of scale.

**7.2 Quenching**

**7.2.1** The time between removal of the test piece from the furnace and the commencement of spraying shall not exceed 5 s.

During its removal from the furnace and positioning in the holder, the test piece shall only be held with the tongs at the end which is not to be quenched either on the flange side or the undercut side.

**7.2.2** The time of spraying shall be at least 10 min. After this time, the cooling of the test piece can be completed by immersing it in cold water.

**8 Preparation for, and measurement of, hardness after quenching**

**8.1** Two flats for measuring the hardness shall be ground on the surface 180° apart and parallel to the axis of the test piece. In the case of test pieces prepared by machining, the two flats shall be at the same distance from the product surface (see Figure 1). They shall be from 0,4 mm to 0,5 mm deep. These flats shall be machined using an

abundant supply of coolant with fine grinding wheel to avoid any heating which is likely to modify the microstructure of the test piece.

**8.2** It should be ascertained, as follows, that no softening has been caused by grinding: immerse the test piece in a 5 % (V/V) nitric acid solution in water until it is completely blackened. The colour obtained shall be uniform.

If there are any stains, indicating the presence of soft spots, two new flats shall be made at 90° and etched as stated above to make sure that these were acceptable. In this case, the hardness measurement shall be carried out on the second set of flats and this fact shall be recorded in the test report.

**8.3** Precautions shall be taken to ensure that the test piece is well supported and is rigidly held during the hardness measurements.

The device for moving the test piece on the hardness testing machine shall allow accurate centring of the flat and spacing of the indentations to within  $\pm 0,1$  mm. The latter are made along the axis of the flat, in accordance with ISO 6508-1, ISO 6508-2 and ISO 6508-3.

**8.3.1** By special agreement, the Rockwell C hardness measurements may be replaced by measurements of Vickers hardness HV 30 in accordance with ISO 6507-1.

**8.3.2** It is necessary to ensure that any raised edges of hardness indentations on the first flat do not influence the measurements on the second flat.

**8.4** The positions of the measurement points shall be such that one or the other of the following two determinations can be made:

- a) drawing of a curve representing variations in hardness (see 8.4.1);
- b) determination of hardness at one or more specified points (see 8.4.2).

#### **8.4.1 Drawing of a curve representing variations in hardness**

**8.4.1.1** In the general case, the distances, expressed in millimetres, of the first eight points taken from the quenched end are as follows (see Figure 5):

1,5 - 3 - 5 - 7 - 9 - 11 - 13 - 15

Subsequent points are, in general, at 5 mm intervals.

**8.4.1.2** In the case of steels of low hardenability, the first measuring point shall be 1,0 mm from the quenched end; the following points shall be spaced at 1 mm intervals to a distance of 11 mm from this end. The last five points shall be, respectively, 13 mm, 15 mm, 20 mm, 25 mm and 30 mm from the same end.

**NOTE** It is realized that the distance between the hardness indentations given in 8.4.1.1 and 8.4.1.2 will not always comply with the minimum distances stated in ISO 6508. For the purposes of this International Standard, however, it is considered that the hardness values obtained will, in general, be sufficiently accurate.

#### **8.4.2 Determination of hardness at specified points**

Determination of hardness may be made at one or more points situated at specified distances from the quenched end and including, or not, the first point specified in 8.4.1.1 and 8.4.1.2.

## **9 Expression of results**

### **9.1 Hardness at any one point**

At each distance  $d$ , the hardness shall be recorded as the mean of the measurements made at this distance  $d$  on each of the two flats specified in 8.1 and the value rounded in principle to 0,5 HRC or 10 HV.

## 9.2 Drawing of the hardness curves

The distances  $d$  shall be plotted on the abscissa and the corresponding hardnesses on the ordinate. It is recommended to use the following scales:

- on the abscissa, either 10 mm corresponding to a distance of 5 mm; or 10 mm corresponding to a distance 1 mm for steels of low hardenability;
- on the ordinate: 10 mm corresponding to 5 HRC or 50 HV.

NOTE When Jominy curves are produced by computer-aided devices, the computer program will scale the axes automatically.

## 9.3 Description of the hardenability characteristics of a particular steel

Use one of the following methods:

- a) drawing of the hardness curve;
- b) statement of the hardness at three points, one point being 1,5 mm (1 mm for low hardenability steels) from the quenched end and the other two points being fixed by special agreement;
- c) statement of the hardness at two points situated at distances fixed by special agreement;
- d) statement of the hardness at one specified distance from the quenched end;
- e) tables of hardness-distance values.

## 9.4 Codification of test result

The test result can be expressed in the following form: the letter J followed by two numbers as follows:

$J_{xx-d}$

where

$xx$  is the hardness, either HRC or HV 30;

$d$  is the distance from the point of measurement to the quenched end, in millimetres.

### EXAMPLES

J35-15 shows that at a distance of 15 mm from the quenched end the hardness is 35 HRC (see Figure 6),

JHV 450-10 shows that at a distance of 10 mm from the quenched end the hardness is 450 HV 30.

NOTE It is also possible to use the code  $Jd = xx$ , see A.2.4.

## 10 Test report

The test report shall contain the following information:

- a) reference to this International Standard, i.e., ISO 642;
- b) grade of the steel;
- c) cast number;
- d) chemical composition;
- e) method of sampling;
- f) conditions for the normalizing treatment and the heating of the test piece;

- g) hardness testing method used;
- h) test result.

NOTE It is recommended to note the water temperature in order to be able to compare the results.

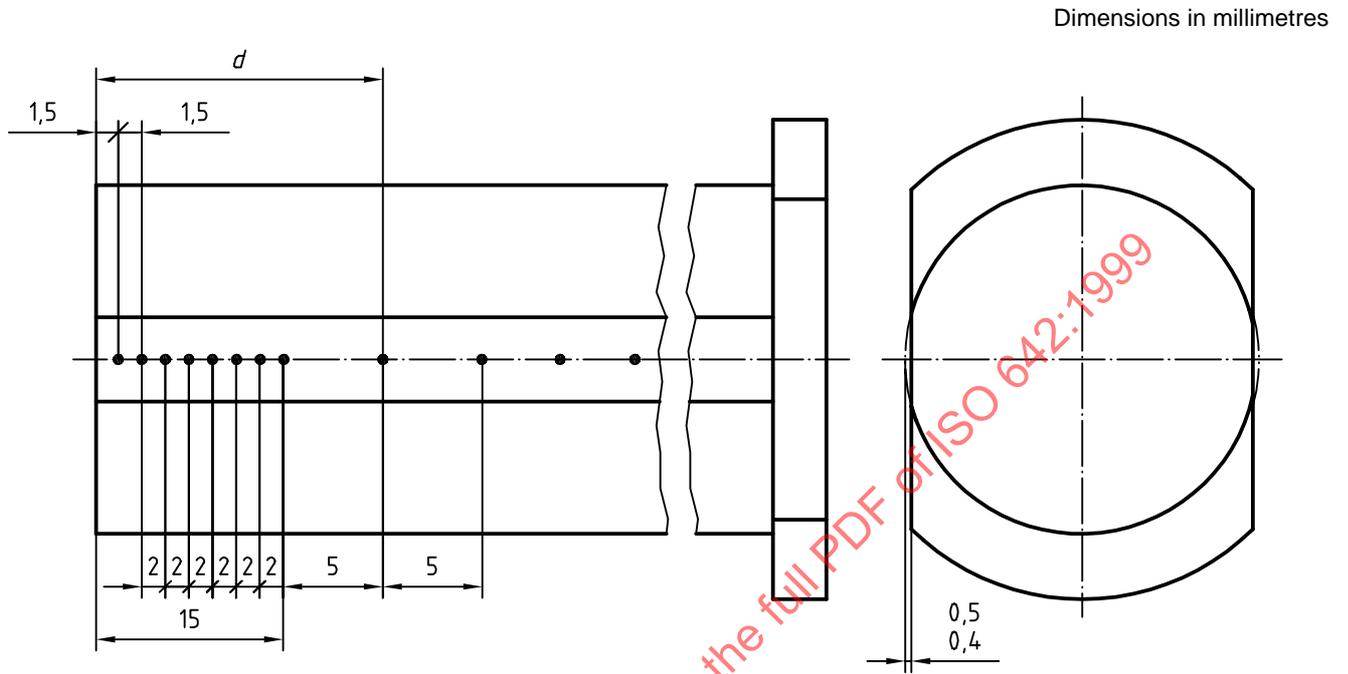


Figure 5 — Preparation of test piece for measurement of hardness, and position of hardness measurement points

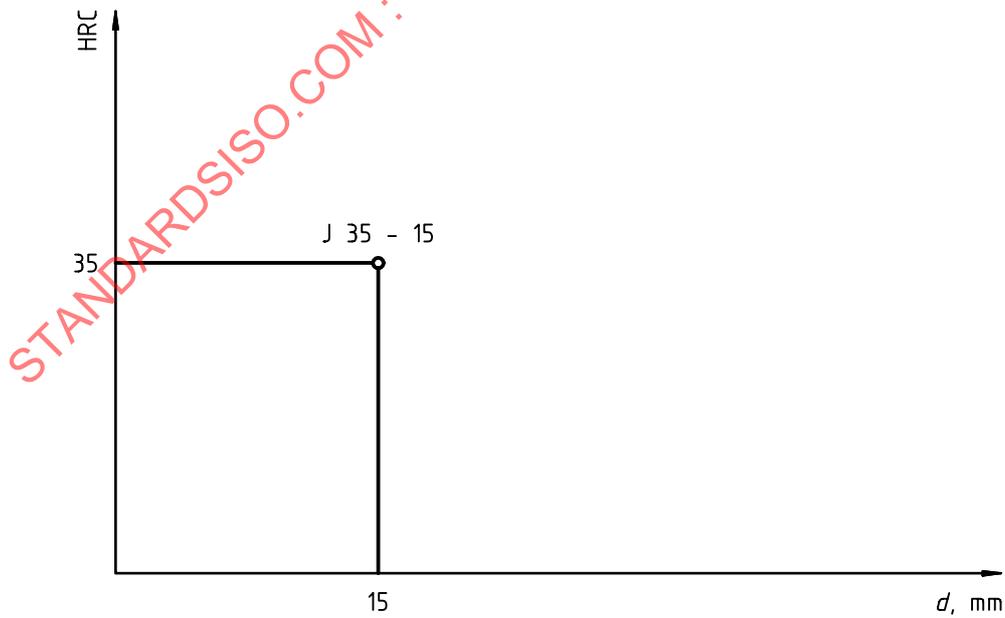


Figure 6 — Hardness at a distance  $d$  of 15 mm

## Annex A (informative)

### Specification for the hardenability of a product

#### A.1 Methods

Use one of the following methods:

- a) specify the end quenching (Jominy test) curve(s) of depth of hardness with:
  - 1) a limiting curve above which the end quenching (Jominy test) curve of depth of hardness of the steel shall lie; or
  - 2) a limiting curve below which the end quenching (Jominy test) curve of depth of hardness of the steel shall lie; or
  - 3) the upper and lower end quenching (Jominy test) curves between which the end quenching (Jominy test) curve of the steel shall lie (see Figure A.1);
- b) specify particular points on the end quenching (Jominy test) curve (which can be):
  - an upper limit; or
  - a lower limit; or
  - a range between the two limits:
    - i) by indicating the distance from the quenched end for a given hardness; or
    - ii) by indicating the hardness at a given distance from the quenched end.

#### A.2 Specifying the hardenability

It is also possible to specify the hardenability as follows.


**A.2.1** J 45-6/18 shows that the hardness reaches a value of 45 HRC at some point between 6 mm and 18 mm from the quenched end (see Figure A.2).

**A.2.2** J 35/48-15 shows that, at a distance of 15 mm from the quenched end the hardness has a value between 35 HRC and 48 HRC (see Figure A.3).

**A.2.3** JHV 340/490-15 shows that, at a distance of 15 mm from the quenched end, the Vickers hardness is between HV 340 and HV 490.

**A.2.4** In some countries, the following codification is used.

J 15 = 35/45 shows that, at a distance of 15 mm from the quenched end, the HRC value is between 35 and 45.

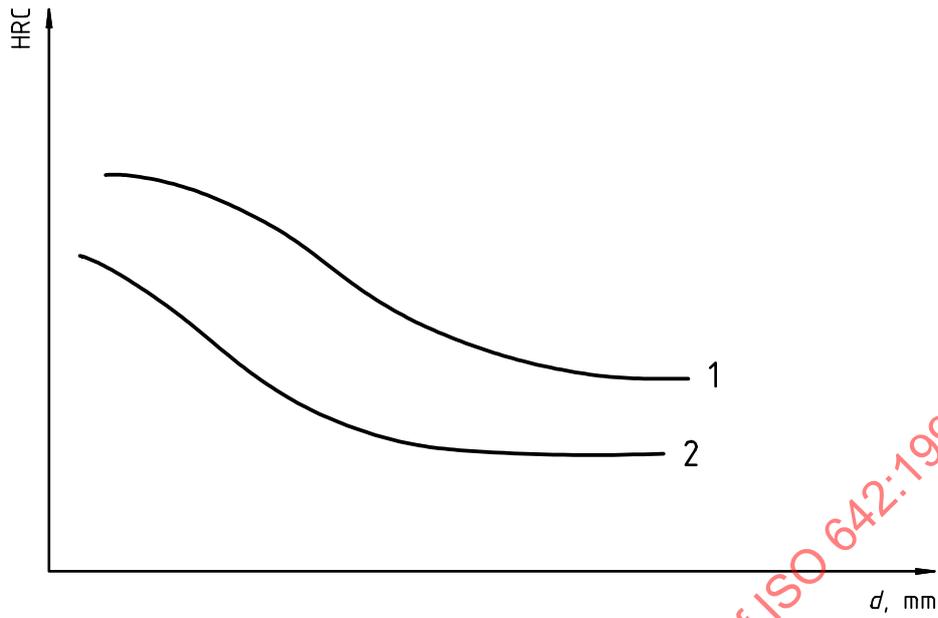

- Key**  
 1 Upper limit  
 2 Lower limit

Figure A.1 — Specification of hardenability by two limiting curves

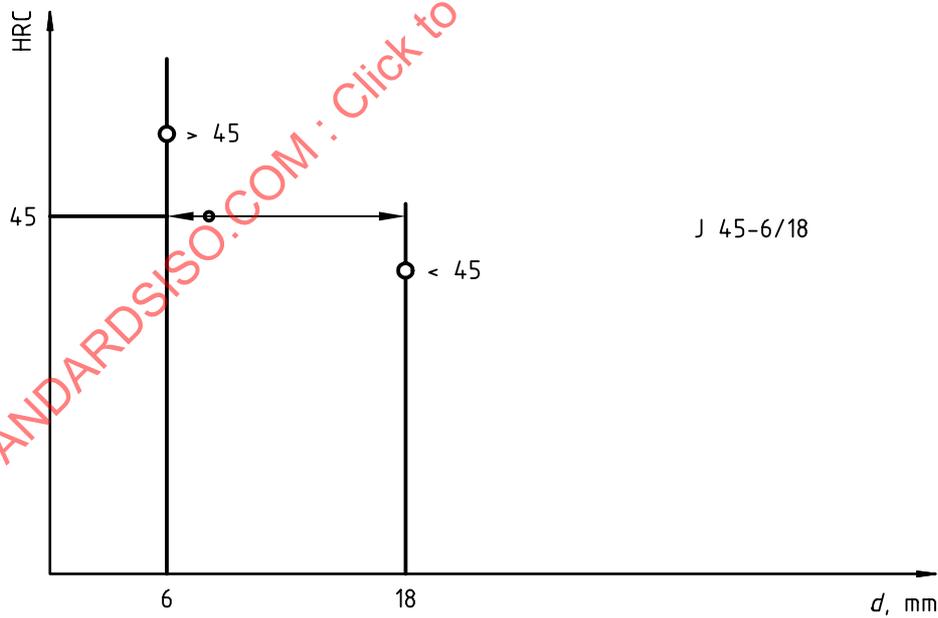


Figure A.2 — Specification of hardenability by a given hardness between two distance limits



Figure A.3 — Specification of hardenability by a range of hardness at a given distance

STANDARDSISO.COM : Click to view the full PDF of ISO 642:1999

## Annex B (informative)

### Additional information to clause 10

In many cases, it could be useful to know the cooling rate on the surface of the test piece.

The conditions of the quenching process defined in clause 6 and in 7.2 permit the cooling rate of the end of the test piece to be considered as constant.

Subject to the fact that one can, at a first approximation, neglect on the one hand the amount of heat produced by structural changes in the steel during cooling and, on the other hand, the differences in thermal conductivity for different grades of steel in relation to a standard test piece, the variations of temperature along the length of the test piece can be expressed in different ways. The following are given as examples for information.

- a) Figure B.1: network of curves giving the ratio  $\theta/\theta_A$  as a function of time

where

$\theta_A$  is the temperature of austenitizing;

$\theta$  is the temperature of points on the surface, situated at certain distances from the quenched end.

- b) Figure B.2: variation of the cooling rates, in degrees Celsius per second, of points on the surface of the Jominy test piece at approximately 700 °C, as a function of their distance from the quenched end.

STANDARDSISO.COM : Click to view the full PDF of ISO 642:1999

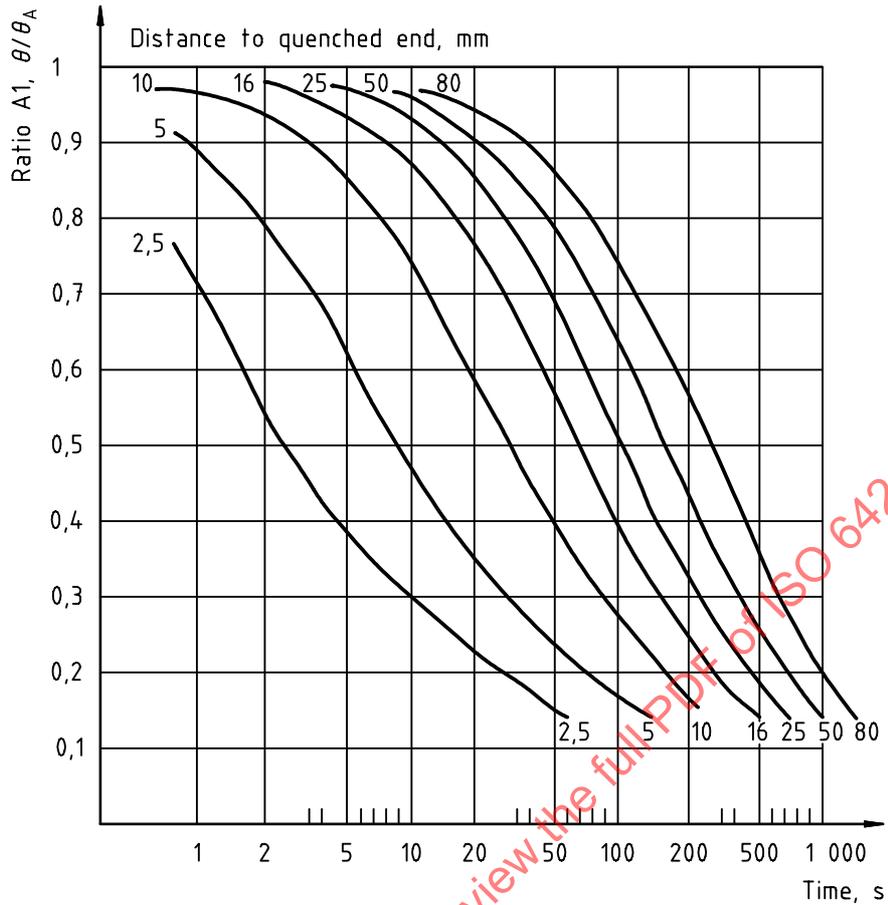


Figure B.1 — Network of curves giving the ratio  $\theta/\theta_A$  as a function of time

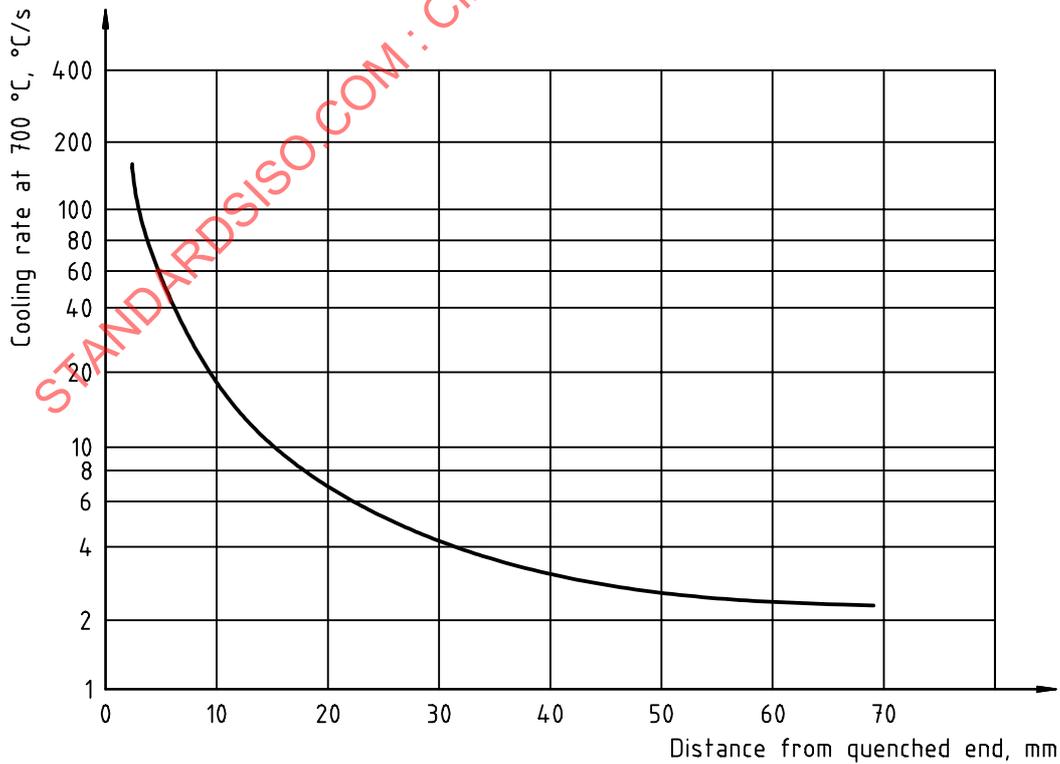


Figure B.2 — Variation of the cooling rates, in degrees Celsius per second, of points on the surface of the Jominy test piece at approximately 700 °C as a function of their distance from the quenched end

## Annex C (informative)

### Calculation of the hardenability

With the aid of computer facilities, calculation models by treatment of numerical data have been developed to determine the Jominy curve from the chemical composition (cast analysis).

These models, duly verified, are based on a great number of test results. The equations used for calculation of the hardenability are different in function of the nature of steel and of their origin and of the used model.

STANDARDSISO.COM : Click to view the full PDF of ISO 642:1999