

# INTERNATIONAL STANDARD



# 923

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

## Coal cleaning tests — Expression and presentation of results

*Essais d'épuration du charbon — Expression et représentation des résultats*

First edition — 1975-12-01

STANDARDSISO.COM : Click to view the full PDF of ISO 923:1975

UDC 662.66 : 622.7 : 620.1 : 001.818

Ref. No. ISO 923-1975 (E)

**Descriptors :** coal, coal preparation, tests, cleaning, test results.

## FOREWORD

ISO (the International Organization for Standardization) is a worldwide federation of national standards institutes (ISO Member Bodies). The work of developing International Standards is carried out through ISO Technical Committees. Every Member Body interested in a subject for which a Technical Committee has been set up has the right to be represented on that Committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the Technical Committees are circulated to the Member Bodies for approval before their acceptance as International Standards by the ISO Council.

Prior to 1972, the results of the work of the Technical Committees were published as ISO Recommendations; these documents are now in the process of being transformed into International Standards. As part of this process, Technical Committee ISO/TC 27 has reviewed ISO Recommendation R 923 and found it technically suitable for transformation. International Standard ISO 923 therefore replaces ISO Recommendation R 923-1969 to which it is technically identical.

ISO Recommendation R 923 was approved by the Member Bodies of the following countries :

Australia	Greece	Spain
Austria	India	Switzerland
Belgium	Iran	Thailand
Bulgaria	Japan	Turkey
Canada	Korea, Rep. of	United Kingdom
Czechoslovakia	Netherlands	U.S.A.
Denmark	New Zealand	U.S.S.R.
Egypt, Arab Rep. of	Poland	Yugoslavia
France	Romania	
Germany	South Africa, Rep. of	

No Member Body expressed disapproval of the Recommendation.

The Member Bodies of the following countries disapproved the transformation of ISO/R 923 into an International Standard :

Czechoslovakia  
Japan

# Coal cleaning tests — Expression and presentation of results

## 0 INTRODUCTION

A number of formulae have been used in different countries for expressing the results of coal cleaning tests and for determining the efficiency of the separation processes (see annex A). Bearing in mind the different purposes for which such tests are carried out, it is considered that no one of these formulae, taken by itself, is adequate. It is, therefore, recommended that four formulae should be used in conjunction for expressing the basic data (see 4.2). In addition, recommendations are made for standard methods of presenting these data in tabular and graphical form (see annexes B and C).

The general adoption of these formulae, tables and graphs should simplify the exchange of information relating to the efficiency and performance of coal preparation plant, and the accumulation of data resulting from their use on a variety of coals treated in different types of machine in different parts of the world should enable them to be simplified at a later date.

## 1 SCOPE

This International Standard outlines the principles on which the expression of the efficiency of operation of coal cleaning plant should be based, states the criteria, coefficients and formulae to be used and also gives methods for tabulation and graphical presentation of the test data.

## 2 FIELD OF APPLICATION

Expressions of the efficiency of coal cleaning processes are required for

- a) the indication of the accuracy (or inaccuracy) of a given separating operation on a particular coal;
- b) the prediction of the probable results of treating different coals by a given separating operation;
- c) the comparison of different separating processes.

## 3 DEFINITIONS

The terms used in this International Standard are defined in ISO/R 1213, *Vocabulary of terms relating to solid mineral fuels — Part I: Terms relating to coal preparation*.

## 4 STANDARD EXPRESSION OF EFFICIENCY

4.1 Many different formulae have been proposed to express the results of coal cleaning tests and the efficiency of the separation processes. Those commonly used are listed in annex A. For the purpose of meeting the requirements stated in clause 2, no one of these formulae, by itself, suffices.

4.2 For a standard expression of efficiency, the following formulae should be used in conjunction:

4.2.1 Separation density expressed as

- a) partition density, and/or
- b) equal errors cut-point (density).

4.2.2 Total of correctly placed material at the separation density, expressed as a percentage of the reconstituted feed, and, where required, the misplaced material in each product at the separation density, expressed as a percentage of the product.

4.2.3 *Écart probable (moyen)* and imperfection.

4.2.4 Ash error or organic efficiency

## 5 TABULATION AND GRAPHICAL PRESENTATION OF TEST RESULTS

The formulae for the expression of efficiency are derived by standard methods of calculation from the basic test data; for convenience, the tables and graphs in which these data are presented should also follow a standard pattern.

Annexes B and C describe and exemplify recommended methods for the tabulation and graphical presentation of test results.

## 6 SIZE OF COAL

In expressing efficiency, it is essential to state the nominal size limits of the coal to which the calculations refer.

## 7 MULTIPLE-PRODUCT SEPARATION

In multiple-product separation, the criteria should be expressed at each separation density (see also annex B, clause B.2).

## ANNEX A

## METHODS OF EXPRESSING EFFICIENCY

	Formula	Derived from	Remarks
A.1	<b>Separation density</b> a) Partition density b) Equal errors cut-point (density)	Partition curves M-curves Washability curves	Describes one characteristic of the separation, but does not indicate its accuracy
A.2	<b>Misplaced material</b>	M-curves Washability curves	Measure of quantity of misplaced material (without reference to its quality) at the separation density
A.3	<b>Total of correctly placed material</b>	M-curves Washability curves	Measure of quantity of correctly placed material (without reference to its quality) at the separation density
A.4	<b>Ash error</b>	M-curves Washability curves	Reflects both the quantity and quality of misplaced material in terms of the specific property of coal (percentage of ash) which the separation is designed to control; measures qualitative efficiency
A.5	<b>Yield error</b>	M-curves Washability curves	Reflects both the quantity and quality of misplaced material and measures quantitative efficiency
A.6	<b>Organic efficiency</b>	M-curves Washability curves	Related to yield error but expressed as a percentage
A.7	<b>Error area</b>	Partition curves	Measure of quantity of misplaced material in terms of density
A.8	<b>Partition coefficients</b>	Partition curves	Special applications only
A.9	<i>Écart probable (moyen)</i>	Partition curves	Gives an indication of the quantitative errors inherent in the separating process at a given separation density
A.10	<b>Imperfection</b>	Partition curves	Modification of <i>écart probable (moyen)</i> to include effect of varying separation density
A.11	<b>Yield loss</b>	Product samples	States results without reference to accuracy of separation

## NOTES

1 **M-curves** and **washability curves** describe graphically the character of the raw coal and of the products, in terms of mass and ash content. **Partition curves** describe only the products and in terms of mass and density; they can be constructed without the necessity to determine ash content.

2 **M-curves** have wider direct applications than **washability curves**, especially, for example, in three-product separations.

3 The *écart probable (moyen)* and **imperfection** reflect the influence of changes in the separation process rather than in the raw coal, in contrast to the formulæ derived from **M-curves** or **washability curves**, which reflect changes in the raw coal as well as in the separation process.

4 The **separation density**, although not a measure of efficiency, is an important characteristic of the separation and is essential to any comprehensive statement of the results of a given test.

5 The **misplaced material** and the **total of correctly placed material** at the **separation density**, the **ash error**, the **yield error**, the **organic efficiency** and the **error area** can all be used for guarantee tests and occasional control tests to give an indication of the accuracy of a given separation on a given coal, and hence of economic efficiency; but they are of little value in the prediction of probable results of cleaning a range of coals by one specific process.

6 **Partition coefficients**, *écart probable (moyen)* and **imperfection** are valuable for the purpose of prediction but do not give an adequate indication of the accuracy of a given separating operation on a particular coal.

## ANNEX B

RECOMMENDATIONS FOR STANDARD METHODS OF PRESENTING COAL  
CLEANING TEST DATA

## B.1 DESCRIPTION OF THE TABLES

B.1.1 Two sets of tables are required (see clause B.4) :

- a) for three-product separation (cleaned coal, middlings and reject);
- b) for two-product separation (cleaned coal and reject).

For convenience, an identical layout has been adopted for both sets of tables, but in those intended for use with two-product separations, the columns which relate only to three-product separation have been struck through so as to avoid confusion.

B.1.2 Each set of tables is presented in two ways :

- a) blank tables, to show the method of printing (see Form 1 and Form 3 in clause B.4);
- b) tables completed, by way of example, by filling in the figures relating to the results of a test on a Baum jig washer (see Form 2 and Form 4 in clause B.4).

B.1.3 For the test described in this example, the washer was supplied with coal sized from 152 mm to 0 (6 in to 0). The figures used refer to the fraction sized between 12,7 mm (1/2 in) and 0,5 mm. The fine material below 0,5 mm was removed from the samples before carrying out float and sink tests, because this fine material presents difficulties in testing. Moreover, the jig is not expected to clean material smaller than 0,5 mm.

B.1.4 For a full analysis of the test, tables similar to those given for the 12,7 mm (1/2 in) – 0,5 mm size would be required for the other sizes of the raw coal, in this instance 152 – 51 mm (6 – 2 in), 51 – 25,4 mm (2 – 1 in), and 25,4 – 12,7 mm (1 – 1/2 in). Such tables would enable the performance on the different sizes to be compared. By adding together the results on the four individual sizes, a further set of tables could be constructed representing the whole of the 152 mm (6 in) – 0,5 mm coal.

B.1.5 In this test, three products were made : cleaned coal, middlings and reject. The reject is the material removed by the primary reject elevator and the middlings is the reject from the secondary reject elevator. The tables headed "three-product separation" are built up from float and sink tests at various relative densities from 1,30 to 2,00 on samples of each of these three products. Although intervals of 0,1 relative density have been used for the example, different ranges and intervals may be required in other cases.


B.1.6 The figures in the tables headed "two-product separation" have been calculated from these same figures on the assumption that the products from both elevators (i.e. the middlings and the reject) were combined so that there were two products only : cleaned coal and a single reject.

B.2 EXPRESSION OF EFFICIENCY IN THE THREE-  
PRODUCT SEPARATION

B.2.1 Three-product separation may be regarded as a combination of two distinct two-product separations (i.e. a low-density cut and a high-density cut), whether these two stages are in fact carried out in different separating vessels or in different parts of the same vessel.

The following diagrams illustrate different combinations of the two stages :

Diagram  
No.

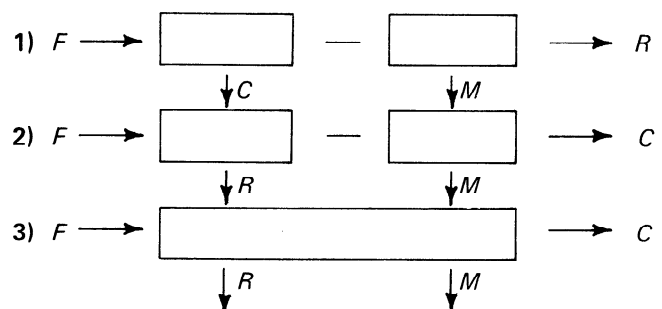

where

- $F$  is the feed (reconstituted raw coal);
- $C$  is the cleaned coal;
- $R$  is the reject;
- $M$  is the intermediate product (middlings).

Diagrams 1 and 2 represent typical arrangements for a two-stage dense medium separation, the only difference being that the low-density cut comes first in diagram 1 and second in diagram 2, while diagram 3 represents a normal three-product jig (or a three-product dense medium separation). The middlings  $M$  may be collected as a separate product, or recirculated, or otherwise dealt with, but provided that any recirculated middlings are included in the reconstituted feed  $F$ , the argument is unaffected.

**B.2.2** The efficiency of a three-product separation may be calculated in two different ways :

- a) *Method A*, by regarding it as two distinct and individual separations, each with its own feed;
- b) *Method B*, by regarding it as a single comprehensive separation, the feed for which is the reconstituted raw coal.

**B.2.2.1** In order to calculate the partition coefficients, the appropriate formulae for these two methods, for the combinations of plant illustrated in the diagrams, are as follows :

**B.2.2.1.1 For diagram 1**

a) <i>Method A</i>	low-density cut	$\frac{100 (M + R)}{C + M + R}$
	high-density cut	$\frac{100 R}{M + R}$
b) <i>Method B</i>	low-density cut	$\frac{100 (M + R)}{C + M + R}$
	high-density cut	$\frac{100 M}{C + M + R}$

**B.2.2.1.2 For diagram 2**

a) <i>Method A</i>	high-density cut	$\frac{100 R}{C + M + R}$
	low-density cut	$\frac{100 M}{C + M}$
b) <i>Method B</i>	high-density cut	$\frac{100 R}{C + M + R}$
	low-density cut	$\frac{100 M}{C + M + R}$

**B.2.2.1.3 For diagram 3**

a) <i>Method A</i>	high-density cut	$\frac{100 R}{C + M + R}$
	low-density cut	$\frac{100 M}{C + M}$
b) <i>Method B</i>	high-density cut	$\frac{100 R}{C + M + R}$
	low-density cut	$\frac{100 (M + R)}{C + M + R}$

**B.2.2.2** While for *Method A* the formulae are identical for diagrams 2 and 3, in the latter case there is no sharp dividing line between the first and second cuts. The first (high-density) cut separates the reject *R* from the

combination of the cleaned coal *C* and middlings *M*, and it is this combination which becomes the feed to the second stage of the separation.

**B.2.2.3 Method A** enables the efficiency of each of the two separations to be studied individually, for only the material actually admitted to the separation is included in the calculation. This is of advantage when considering the performance of each machine or stage in the separation process.

**B.2.2.4 Method B** does not show up so emphatically the actual performance of the second machine or stage, but by referring each separation back to the reconstituted raw feed it facilitates comparisons of the efficiency of the whole separation process in terms of the results on the original raw coal. (The sequence of operations included in this complete process may include steps not shown in diagrams 1 to 3, for example crushing of the middlings and its recirculation to the feed, which is common in jig washing and may also occur in dense medium separation.)

**B.2.3** It is essential, whenever the efficiency of a three-product separation is expressed (for example in descriptions of plant and efficiency statements and guarantees), that it should be clearly stated which of these two bases has been used for the calculation. To facilitate this, it is proposed that *Method A* should be described as the **equipment performance basis**, and *Method B* as the **coal performance basis**.

**B.2.4** The attached tables for the three-product separations are drawn up on the **coal performance basis**. When calculations are made on the **equipment performance basis**, it is recommended that two-product tables should be used (one for each stage). It is possible, however, to deduce the results from the three-product table; thus, partition coefficients for the second cut would be calculated on the **equipment performance basis** as follows :

- For diagram 1 (see B.2.1), column (12) would be calculated from (7)/(9) instead of (7)/(10).
- For diagrams 2 and 3 (see B.2.1), column (13) would be calculated from (6)/(8) instead of (9)/(10).

**B.3 DESCRIPTION OF THE GRAPHS** (see annex C)

**B.3.1** In order to calculate the efficiency by the four formulae proposed (see 4.2), the data in these tables must be represented in graphs. Graphs relating to the test results are shown in figures 1 to 4. The graphs have been prepared from the data for three-product separation; but the curves for the low-density cut apply to the two-product example.

**B.3.2** Figure 1 has been drawn to a scale such that 0,2 unit on the relative density axis equals 10 % on the partition coefficient axis. It is proposed to standardize this relation for drawing partition curves, when using (as in figure 1) linear co-ordinates, but similar standard scales for the other



curves are not at present considered to be practicable. The curves can also be drawn using other than linear co-ordinates.

**B.3.3** The following sub-clauses explain the construction and use of the graphs in figures 1 to 4 :

**B.3.3.1 Partition curves (three-product)** (see figure 1)

**B.3.3.1.1** The partition coefficients in columns (12) and (13) are plotted against the mean of the relative densities shown in the table for each fraction.

**B.3.3.1.2** The curve on the right represents the high-density cut because it refers to the removal of the final reject.

**B.3.3.1.3** The table columns from which the coefficients are extracted are shown on each curve.

**B.3.3.1.4** The relative density at which the curves cross 50 % is by definition the **partition density**. Similarly *écart probable (moyen) (Epm)* is defined in terms of the relative densities  $d_{25}$  and  $d_{75}$  at which the curves cross 25 % and 75 % respectively. The imperfection (I) is derived from these as shown.

**B.3.3.2 Ash error and organic efficiency** (see figure 2)

**B.3.3.2.1** The curve shows the cumulative mass on the reconstituted feed plotted against the cumulative ash per cent, the figures being from columns (43) and (45).

**B.3.3.2.2** The point X represents the actual yield and ash for the high-density cut (total cleaned coal and middlings), and the point Y represents those for the low-density cut (total cleaned coal).

**B.3.3.2.3** Regarding point X :

- the actual ash is 5,61 % and the theoretical float and sink ash for the actual yield of 93,4 % as given by the curve is 5,05 %. The ash error is the difference between these two ash percentages.
- the actual yield is 93,40 % at 5,61 % ash. The theoretical float and sink yield for 5,61 % ash is given by

the curve as 94,60 %. The organic efficiency is derived from the ratio of these two yields.

**B.3.3.2.4** Similar considerations apply to point Y.

**B.3.3.3 Correctly placed (and misplaced) material – high-density cut** (see figure 3)

**B.3.3.3.1** The two lower curves show the amounts of misplaced material in the reject (column 18) and the cleaned coal plus middlings product (column 17) – the fraction which in this example goes forward for further treatment. The upper curve shows the sum or total of the misplaced material in these two products combined (column 19). The total amount (percentage) of correctly placed material (100 minus misplaced material) is read from the scale on the right-hand side of the graph.

**B.3.3.3.2** The equal errors cut-point (density) is the relative density at which the two lower curves intersect; in this example this density is 1,770. The partition density is 1,835.

**B.3.3.3.3** The relative densities of 1,770 and 1,835 correspond respectively to 96,6 and 96,7 % for the amounts of correctly placed material.

**B.3.3.4 Correctly placed (and misplaced) material – low-density cut** (see figure 4)

The same considerations apply as for the high-density cut, the amounts of misplaced materials in each product being plotted from columns (23) and (24) and the total from column (25). The equal errors cut-point and the partition densities are 1,400 and 1,505 and the amounts of correctly placed material 89,9 and 91,0 % respectively.

**B.3.4** The curves in figures 1 to 4 have been drawn on the coal performance basis, all yields being expressed as a percentage of the reconstituted raw coal. On the equipment performance basis, the washing operation being regarded as two distinct two-product separations, the construction of the curves follows exactly the same method as for any two-product separation and presents no difficulties. The curves which apply to the high-density cut (figure 1 : lower curve; figure 2 : point X; figure 3 : upper curve) are identical for both bases.

## B.4 TABLES

FORM 1 — Tables for three-product separation

Data required for calculation of efficiency ~~two~~<sup>three</sup> product separation

Reference :		Date of test :				Name of plant :					
Test details		Tonnages				Summary of results					
Size of coal analysed mm/in		Raw coal treated	Size analysed		Total feed to plant		<del>(1) Single cut : Actual products (see footnote) Cleaned coal Reject</del>				
Size of feed to plant mm/in			Tons	%	Tons	%	(1) High-density cut : Cleaned coal + Middlings/Reject (2) Low-density cut : Cleaned coal/Middlings + Reject				
Type of cleaning unit											
Rated capacity ton/h		Products Cleaned coal Middlings Reject					Separating density		Correctly placed material %		
Seam(s) treated							(1)	(2)	(1)	(2)	
Actual testing period	h min	Feed rate ton/h Basis of masses : Dry* Air dry* As received*				Partition					
						Equal errors					
						Epm					
Total stoppages	h min					Imperfection					
						Ash error					
Net testing time	h min	* Cross out those which do NOT apply				Organic efficiency		%	%		

NOTE — For a two-product separation, the products are named *cleaned coal* and *reject* although the actual products may in fact be cleaned coal and reject *or* cleaned coal and middlings *or* middlings and reject.



FORM 1 — Tables for three-product separation (continued)

TABLE 1 — Distribution by mass of products and reconstituted feed

Relative density fractions	Analysis by mass			Percentage of feed			Cleansed coal + middlings : high density cut	Middlings + reject : low density cut	Reconstituted feed %	Relative density (nominal)	Partition coefficient	
	Cleansed coal %	Middlings %	Reject %	Cleansed coal	Middlings	Reject					High-density cut	Low-density cut
				X (2)	X (3)	X (4)	(5)+(6)	(6)+(7)	(5)+(6) +(7)		(7)/(10) × 100	(9)/(10) × 100
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)	(11)	(12)	(13)
Totals	100,00	100,00	100,00						100,00	—	—	—

TABLE 2 – **Correctly placed material** (100 % minus misplaced material)

[illegible]

\_\_\_\_\_

44

## FORM 2 — Example for three-product separation

Data required for calculation of efficiency ~~two~~<sup>three</sup> product separation

Reference : <i>XTD/41/B</i>		Date of test : <i>1975-07-16</i>				Name of plant : <i>Britannia Washery</i>					
Test details		Tonnages				Summary of results					
Size of coal analysed mm/in	<i>12,7 mm (<math>\frac{1}{2}</math> in) to 0,5 mm</i>	Raw coal treated	Size analysed		Total feed to plant		<del>(1) Single cut : Actual products (see footnote) Cleaned coal Reject</del>				
Size of feed to plant mm/in	<i>152 mm to 0 (6 in to 0)</i>		Tons	%	Tons	%	(1) High-density cut : Cleaned coal + Middlings/Reject (2) Low-density cut : Cleaned coal/Middlings + Reject				
Type of cleaning unit	<i>Baum jig</i>										
Rated capacity ton/h	<i>75</i>	Products					Separating density		Correctly placed material %		
Seam(s) treated	<i>Tip Top</i>	Cleaned coal	<i>62,0</i>	<i>83,6</i>	<i>174,3</i>	<i>75,1</i>					
		Middlings	<i>8,1</i>	<i>10,8</i>	<i>31,6</i>	<i>13,6</i>		(1)	(2)	(1)	(2)
		Reject	<i>4,9</i>	<i>6,6</i>	<i>26,1</i>	<i>11,3</i>	Partition	<i>1,835</i>	<i>1,505</i>	<i>96,7</i>	<i>91,0</i>
							Equal errors	<i>1,770</i>	<i>1,400</i>	<i>96,6</i>	<i>89,9</i>
Actual testing period	<i>3 h 25 min</i>	Feed rate ton/h	<i>67,9</i>				<i>Epm</i>	<i>0,185</i>	<i>0,115</i>		
		Basis of masses : Dry*					Imperfection	<i>0,22</i>	<i>0,23</i>		
		<del>Air dry*</del>									
		<del>As received*</del>									
Total stoppages	<i>0 h 0 min</i>						Ash error	<i>0,56</i>	<i>1,35</i>		
Net testing time	<i>3 h 25 min</i>	*Cross out those which do NOT apply					Organic efficiency	<i>98,7%</i>	<i>92,6%</i>		

NOTE — For a two-product separation, the products are named *cleaned coal* and *reject* although the actual products may in fact be *cleaned coal* and *reject* or *cleaned coal* and *middlings* or *middlings* and *reject*.

TABLE 1 — Distribution by mass of products and reconstituted feed

Relative density fractions	Analysis by mass			Percentage of feed			Cleaned coal + middlings : high-density cut	Middlings + reject : low-density cut	Reconstituted feed %	Relative density (nominal)	Partition coefficient	
	Cleaned coal %	Middlings %	Reject %	Cleaned coal	Middlings	Reject					High-density cut	Low-density cut
				0,826X (2)	0,103X (3)	0,066X (4)	(5)+(6)	(6)+(7)	(5)+(6) +(7)		(7)/(10) × 100	(9)/(10) × 100
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)	(11)	(12)	(13)
Under 1,30	83,34	26,84	3,92	68,83	2,89	0,26	71,72	3,15	71,98	?	0,36	4,39
1,30–1,40	10,50	16,08	2,21	8,67	1,74	0,15	10,41	1,89	10,56	1,35	1,42	17,80
1,40–1,50	3,35	14,43	1,79	2,77	1,56	0,12	4,33	1,68	4,45	1,45	2,70	37,75
1,50–1,60	1,79	18,86	4,27	1,48	2,04	0,28	3,52	2,32	3,80	1,55	7,37	61,05
1,60–1,70	0,30	8,44	8,26	0,25	0,91	0,55	1,16	1,46	1,71	1,65	32,16	85,38
1,70–1,80	0,16	5,63	6,21	0,13	0,61	0,41	0,74	1,02	1,15	1,75	35,65	88,70
1,80–1,90	0,07	3,58	7,47	0,06	0,39	0,49	0,45	0,88	0,94	1,85	52,13	93,62
1,90–2,00	0,07	2,05	8,09	0,06	0,22	0,53	0,28	0,75	0,81	1,95	65,43	92,59
Over 2,00	0,42	4,09	57,78	0,35	0,44	3,81	0,79	4,25	4,60	?	82,83	92,39
Totals	100,00	100,00	100,00	82,60	10,80	6,60	93,40	17,40	100,00	—	—	—

TABLE 2 — Correctly placed material (100 % minus misplaced material)

High-density cut						Low-density cut					
% of feed		Relative density	Misplaced material			% of feed		Relative density	Misplaced material		
Cleaned coal + middlings	Reject		Sinks in cleaned coal + middlings	Floats in reject	Total	Cleaned coal	Middlings + reject		Sinks in cleaned coal	Floats in middlings + reject	Total
as (8)	as (7)		↑ Σ (14)	↓ Σ (15)	(17)+(18)	as (5)	as (9)		↑ Σ (20)	↓ Σ (21)	(23)+(24)
(14)	(15)	(16)	(17)	(18)	(19)	(20)	(21)	(22)	(23)	(24)	(25)
71,72	0,26	1,30 1,40 1,50 1,60 1,70 1,80 1,90 2,00	93,40	0,00	93,40	68,83	3,15	1,30 1,40 1,50 1,60 1,70 1,80 1,90 2,00	82,60	0,00	82,60
10,41	0,15		21,68	0,26	21,94	8,67	1,89		13,77	3,15	16,92
4,33	0,12		11,27	0,41	11,68	2,77	1,68		5,10	5,04	10,14
3,52	0,28		6,94	0,53	7,47	1,48	2,32		2,33	6,72	9,05
1,16	0,55		3,42	0,81	4,23	0,25	1,46		0,85	9,04	9,89
0,74	0,41		2,26	1,36	3,62	0,13	1,02		0,60	10,50	11,10
0,45	0,49		1,52	1,77	3,29	0,06	0,88		0,47	11,52	11,99
0,28	0,53		1,07	2,26	3,33	0,06	0,75		0,41	12,40	12,81
0,79	3,81		0,79	2,79	3,58	0,35	4,25		0,35	13,15	13,50
			0,00	6,60	6,60				0,00	17,40	17,40

## FORM 2 — Example for three-product separation (concluded)

TABLE 3 — Ash content of products and reconstituted feed

Relative density fractions	Cleaned coal			Middlings			Reject			Reconstituted feed	
	Mass % of feed	Ash %	Quantity of ash	Mass % of feed	Ash %	Quantity of ash	Mass % of feed	Ash %	Quantity of ash	Mass % of feed	Quantity of ash
as (1)	as (5)	Analysis	(27)×(28)	as (6)	Analysis	(30)×(31)	as (7)	Analysis	(33)×(34)	(27)+(30)+(33)	(29)+(32)+(35)
(26)	(27)	(28)	(29)	(30)	(31)	(32)	(33)	(34)	(35)	(36)	(37)
Under 1,30	68,83	1,4	96,36	2,89	1,6	4,64	0,26	1,4	0,36	71,98	101,34
1,30–1,40	8,67	7,6	65,89	1,74	7,7	13,40	0,15	8,9	1,33	10,56	80,62
1,40–1,50	2,77	15,9	44,04	1,56	18,4	28,70	0,12	18,0	2,16	4,45	74,90
1,50–1,60	1,48	28,6	42,33	2,04	30,4	62,02	0,28	28,3	7,92	3,80	112,27
1,60–1,70	0,25	36,6	9,15	0,91	37,0	33,67	0,55	37,8	20,79	1,71	63,61
1,70–1,80	0,13	41,6	5,41	0,61	42,6	25,99	0,41	45,8	18,78	1,15	50,18
1,80–1,90	0,06	46,4	2,78	0,39	49,0	19,11	0,49	54,4	26,66	0,94	48,55
1,90–2,00	0,06	57,8	3,47	0,22	57,5	12,65	0,53	59,9	31,75	0,81	47,87
Over 2,00	0,35	69,2	24,22	0,44	68,8	30,27	3,81	72,3	275,46	4,60	329,95
Total	82,60	3,56	293,65	10,80	21,34	230,43	6,60	58,4	385,21	100,00	909,29
Total cleaned coal (27) + middlings (30)	93,40	5,61	524,03								
Total middlings (30) + reject (33)							17,40	35,4	615,64		

TABLE 4 — Reconstituted feed

Relative density fractions	Reconstituted feed			Relative density	Cumulative floats			Cumulative sinks		
	Mass %	Quantity of ash	Ash		Mass % of feed	Quantity of ash	Ash %	Mass % of feed	Quantity of ash	Ash %
as (1)	as (36)	as (37)	(40)/(39)		↓ Σ (39)	↓ Σ (40)	(44)/(43)	↑ Σ (39)	↑ Σ (40)	(47)/(46)
(38)	(39)	(40)	(41)	(42)	(43)	(44)	(45)	(46)	(47)	(48)
Under 1,30	71,98	101,34	1,41					100,00	909,29	9,09
1,30–1,40	10,56	80,62	7,63	1,30	71,98	101,34	1,41	28,02	807,85	28,83
1,40–1,50	4,45	74,90	16,83	1,40	82,54	181,96	2,20	17,46	727,33	41,66
1,50–1,60	3,80	112,27	29,54	1,50	86,99	256,86	2,95	13,01	652,43	50,15
1,60–1,70	1,71	63,61	37,20	1,60	90,79	369,13	4,07	9,21	540,16	58,65
1,70–1,80	1,15	50,18	43,63	1,70	92,50	432,74	4,68	7,50	476,55	63,54
1,80–1,90	0,94	48,55	51,65	1,80	93,65	482,92	5,16	6,35	426,37	67,14
1,90–2,00	0,81	47,87	59,10	1,90	94,59	531,47	5,62	5,41	377,82	69,84
Over 2,00	4,60	329,95	71,73	2,00	95,40	579,34	6,07	4,60	329,95	71,73
Total	100,00	909,29	9,09							

## FORM 3 — Tables for two-product separation

Data required for calculation of efficiency ~~three~~ product separation  
two

Reference :		Date of test :				Name of plant :			
Test details		Tonnages				Summary of results			
Size of coal analysed mm/in		Raw coal treated	Size analysed		Total feed to plant		(1) Single cut : Actual products (see footnote) Cleaned coal Reject		
Size of feed to plant mm/in			Tons	%	Tons	%	<del>(1) High-density cut : Cleaned coal + Middlings/Reject (2) Low density cut : Cleaned coal/Middlings + Reject</del>		
Type of cleaning unit									
Rated capacity ton/h		Products						Separating density	Correctly placed material %
Seam(s) treated		Cleaned coal						(1)	(2)
		Middlings							
		Reject							
Actual testing period	h min	Feed rate ton/h Basis of masses : Dry* Air dry* As received*				Partition			
						Equal errors			
Total stoppages	h min					Epm			
						Imperfection			
Net testing time	h min	*Cross out those which do NOT apply				Ash error			
						Organic efficiency		%	%

NOTE — For a two-product separation, the products are named *cleaned coal* and *reject* although the actual products may in fact be cleaned coal and reject or cleaned coal and middlings or middlings and reject.



FORM 3 — Tables for two-product separation (continued)

TABLE 1 – Distribution by mass of products and reconstituted feed

Relative density fractions	Analysis by mass			Percentage of feed			Cleaned coal + middlings :	Middlings + reject :	Reconstituted feed %	Relative density (nominal)	Partition coefficient	
	Cleaned coal %	Middlings %	Reject %	Cleaned coal	Middlings	Reject	high-density cut	low-density cut			High-density cut	Low-density cut
				X	X	X	(5)+(6)	(6)+(7)			(5)+(6)+(7)	(7)/(10) × 100
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)	(11)	(12)	(13)

**TABLE 2 – Correctly placed material (100 % minus misplaced material)**

[illegible]



TABLE 3 – Ash content of products and reconstituted feed

Relative density fractions	Cleaned coal			Middlings			Reject			Reconstituted feed	
	Mass % of feed	Ash %	Quantity of ash	Mass % of feed	Ash %	Quantity of ash	Mass % of feed	Ash %	Quantity of ash	Mass % of feed	Quantity of ash
as (1)	as (5)	Analysis	(27)×(28)	as (6)	Analysis	(30)×(31)	as (7)	Analysis	(33)×(34)	(27)+ <del>(30)</del> +(33)	(29)+ <del>(32)</del> +(35)
(26)	(27)	(28)	(29)	(30)	(31)	(32)	(33)	(34)	(35)	(36)	(37)
Total										100,00	
Total cleaned coal (27) + middlings (30)											
Total middlings (30) + reject (33)											

**TABLE 4 – Reconstituted feed**

[illegible]

## FORM 4 — Example for two-product separation

Data required for calculation of efficiency ~~three~~  
two product separation

Reference : <i>XTD/41/B</i>		Date of test : <i>1975-07-16</i>				Name of plant : <i>Britannia Washery</i>				
Test details		Tonnages				Summary of results				
Size of coal analysed in/mm	<i>12,7 mm (<math>\frac{1}{2}</math> in) to 0,5 mm</i>	Raw coal treated	Size analysed		Total feed to plant		(1) Single cut : Actual products (see footnote) Cleaned coal Reject			
Size of feed to plant in/mm	<i>152 mm to 0 (6 in to 0)</i>		Tons	%	Tons	%	<del>(1) High density cut : Cleaned coal + Middlings/Reject (2) Low-density cut : Cleaned coal/Middlings + Reject</del>			
Type of cleaning unit	<i>Baum jig</i>		<i>75,0</i>	<i>100,0</i>	<i>232,0</i>	<i>100,0</i>				
Rated capacity ton/h	<i>75</i>	Products					Separating density		Correctly placed material %	
Seam(s) treated	<i>Tip Top</i>	Cleaned coal	<i>62,0</i>	<i>82,6</i>	<i>174,3</i>	<i>75,1</i>				
		Middlings					(1)	(2)	(1)	(2)
		Reject	<i>13,0</i>	<i>17,4</i>	<i>57,7</i>	<i>24,9</i>	Partition	<i>1,505</i>		<i>91,0</i>
							Equal errors	<i>1,400</i>		<i>89,9</i>
Actual testing period	<i>3 h 25 min</i>	Feed rate ton/h	<i>67,9</i>				<i>Epm</i>	<i>0,115</i>		
		Basis of masses : Dry*					Imperfection	<i>0,23</i>		
		<del>Air dry*</del>								
Total stoppages	<i>0 h 0 min</i>	<del>As received*</del>					Ash error	<i>1,35</i>		
Net testing time	<i>3 h 25 min</i>	*Cross out those which do NOT apply					Organic efficiency	<i>92,6%</i>	<i>%</i>	

NOTE — For a two-product separation, the products are named *cleaned coal* and *reject* although the actual products may in fact be cleaned coal and reject or cleaned coal and middlings or middlings and reject.

## FORM 4 — Example for two-product separation (continued)

TABLE 1 — Distribution by mass of products and reconstituted feed

Relative density fractions	Analysis by mass			Percentage of feed			Cleansed coal + middlings : high-density cut	Middlings + reject : low-density cut	Reconstituted feed %	Relative density (nominal)	Partition coefficient	
	Cleansed coal %	Middlings %	Reject %	Cleansed coal	Middlings	Reject					High-density cut	Low-density cut
				$0,826 \times$ (2)	$\times$ (3)	$0,174 \times$ (4)	(5)+(6)	(6)+(7)	(5)+(6)+(7)		$(7)/(10) \times 100$	$(9)/(10) \times 100$
(1)	(2)	(3)	(4)	(5)	(6)	(7)	(8)	(9)	(10)	(11)	(12)	(13)
Under 1,30	83,34		18,15	68,83		3,15			71,98	?	4,39	
1,30–1,40	10,50		10,82	8,67		1,89			10,56	1,35	17,80	
1,40–1,50	3,35		9,64	2,77		1,68			4,45	1,45	37,75	
1,50–1,60	1,79		13,33	1,48		2,32			3,80	1,55	61,05	
1,60–1,70	0,30		8,37	0,25		1,46			1,71	1,65	85,38	
1,70–1,80	0,16		5,85	0,13		1,02			1,15	1,75	88,70	
1,80–1,90	0,07		5,05	0,06		0,88			0,94	1,85	93,62	
1,90–2,00	0,07		4,34	0,06		0,75			0,81	1,95	92,68	
Over 2,00	0,42		24,45	0,35		4,25			4,60	?	92,39	
Totals	100,00	100,00	100,00	82,60		17,40			100,00	—	—	—

TABLE 2 — Correctly placed material (100 % minus misplaced material)

High-density cut						Low-density cut					
% of feed		Relative density	Misplaced material			% of feed		Relative density	Misplaced material		
Cleansed coal + middlings	Reject		Sinks in cleansed coal + middlings	Floats in reject	Total	Cleansed coal	Middlings * reject		Sinks in cleansed coal	Floats in middlings + reject	Total
as (8)	as (7)		$\uparrow \Sigma$ (14)	$\downarrow \Sigma$ (15)	(17)+(18)	as (5)	as (9)		$\uparrow \Sigma$ (20)	$\downarrow \Sigma$ (21)	(23)+(24)
(14)	(15)	(16)	(17)	(18)	(19)	(20)	(21)	(22)	(23)	(24)	(25)
						68,83	3,15		82,60	0,00	82,60
						8,67	1,89	1,30	13,77	3,15	16,92
						2,77	1,68	1,40	5,10	5,04	10,14
						1,48	2,32	1,50	2,33	6,72	9,05
						0,25	1,46	1,60	0,85	9,04	9,89
						0,13	1,02	1,70	0,60	10,50	11,10
						0,06	0,88	1,80	0,47	11,52	11,99
						0,06	0,75	1,90	0,41	12,40	12,81
						0,35	4,25	2,00	0,35	13,15	13,50
									0,00	17,40	17,40

FORM 4 – Example for two-product separation (concluded)

TABLE 3 – Ash content of products and reconstituted feed

Relative density fractions	Cleaned coal			Middlings			Reject			Reconstituted feed	
	Mass % of feed	Ash %	Quantity of ash	Mass % of feed	Ash %	Quantity of ash	Mass % of feed	Ash %	Quantity of ash	Mass % of feed	Quantity of ash
as (1)	as (5)	Analysis	(27)×(28)	as (6)	Analysis	(30)×(31)	as (7)	Analysis	(33)×(34)	(27)+ <del>(30)</del> + <del>(33)</del>	(29)+ <del>(31)</del> + <del>(35)</del>
(26)	(27)	(28)	(29)	(30)	(31)	(32)	(33)	(34)	(35)	(36)	(37)
Under 1,30	68,83	1,4	96,36				3,15	1,6	4,98	71,98	101,34
1,30–1,40	8,67	7,6	65,89				1,89	7,8	14,73	10,56	80,62
1,40–1,50	2,77	15,9	44,04				1,68	18,4	30,86	4,45	74,90
1,50–1,60	1,48	28,6	42,33				2,32	30,1	69,94	3,80	112,27
1,60–1,70	0,25	36,6	9,15				1,46	37,3	54,46	1,71	63,61
1,70–1,80	0,13	41,6	5,41				1,02	43,9	44,77	1,15	50,18
1,80–1,90	0,06	46,4	2,78				0,88	52,0	45,77	0,94	48,55
1,90–2,00	0,06	57,8	3,47				0,75	59,2	44,40	0,81	47,87
Over 2,00	0,35	69,2	24,22				4,25	71,9	305,73	4,60	329,95
Total	82,60	33,56	293,65				17,40	35,4	615,64	100,00	909,29
Total cleaned coal (27) + middlings (30)											
Total middlings (30) + reject (33)											

TABLE 4 – Reconstituted feed

Relative density fractions	Reconstituted feed			Relative density	Cumulative floats			Cumulative sinks		
	Mass %	Quantity of ash	Ash %		Mass % of feed	Quantity of ash	Ash %	Mass % of feed	Quantity of ash	Ash %
as (1)	as (36)	as (37)	(40)/(39)		↓ Σ (39)	↓ Σ (40)	(44)/(43)	↑ Σ (39)	↑ Σ (40)	(47)/(46)
(38)	(39)	(40)	(41)	(42)	(43)	(44)	(45)	(46)	(47)	(48)
Under 1,30	71,98	101,34	1,41					100,00	909,29	9,09
1,30–1,40	10,56	80,62	7,63	1,30	71,98	101,34	1,41	28,02	807,85	28,83
1,40–1,50	4,45	74,90	16,83	1,40	82,54	181,96	2,20	17,46	727,33	41,66
1,50–1,60	3,80	112,27	29,54	1,50	86,99	256,86	2,95	13,01	652,43	50,15
1,60–1,70	1,71	63,61	37,20	1,60	90,79	369,13	4,07	9,21	540,16	58,65
1,70–1,80	1,15	50,18	43,63	1,70	92,50	432,74	4,68	7,50	476,55	63,54
1,80–1,90	0,94	48,55	51,65	1,80	93,65	482,92	5,16	6,35	426,37	67,14
1,90–2,00	0,81	47,87	59,10	1,90	94,59	531,47	5,62	5,41	377,82	69,84
Over 2,00	4,60	329,95	71,73	2,00	95,40	570,34	6,07	4,60	329,95	71,73
					100,00	909,29	9,09			
Total	100,00	909,29	9,09							