

Issued 1968-10  
Revised 2004-04

Superseding J365 AUG1994

**Method of Testing Resistance to Scuffing of Trim Materials****1. Scope**

This test can be used to determine the resistance to scuffing of test specimens such as fiberboards, fabrics, vinyl-coated fabrics, leathers, and similar trim materials.

**2. References**

There are no referenced publications specified herein.

**3. Materials and Equipment Required****3.1 Abrader**

Taber Model 5150 or equivalent.

**3.2 Specimen Holder**

108 mm OD.

**3.3 Hold-Down Ring**

108 mm OD.

**3.4 Rubber Pad****3.5 Clamp Plate**

54 mm OD for fabrics, leather, coated fabrics, and similar flexible materials. 32 mm OD for carpets and other floor covering materials.

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

Copyright © 2004 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.

**TO PLACE A DOCUMENT ORDER:** Tel: 877-606-7323 (inside USA and Canada)

Tel: 724-776-4970 (outside USA)

Fax: 724-776-0790

Email: [custsvc@sae.org](mailto:custsvc@sae.org)

<http://www.sae.org>

**SAE WEB ADDRESS:**

### 3.6 Scuff Fixture

The special scuff fixture head, weight, and other components are shown in Figure 1 and are assembled as shown in Figure 2. The scuff fixture is attached to the abrader as shown in Figure 3. The scuff head is held at a 110 degree angle. The vertical centerline of the scuff head is 32 mm from the specimen holder center pin. The tip is centered under the 0.9 kg weight and in a horizontal alignment with the center pin as shown in Figure 3.

NOTE—The attachment bracket shown in Figure 1, detail 8 may be modified for other abrader models, provided the scuff head position is maintained and test results correlate.

The scuff head tip shown in Figure 1, detail 11 must be frequently checked for dimensions and reground or replaced if found to deviate from the specified tolerances.

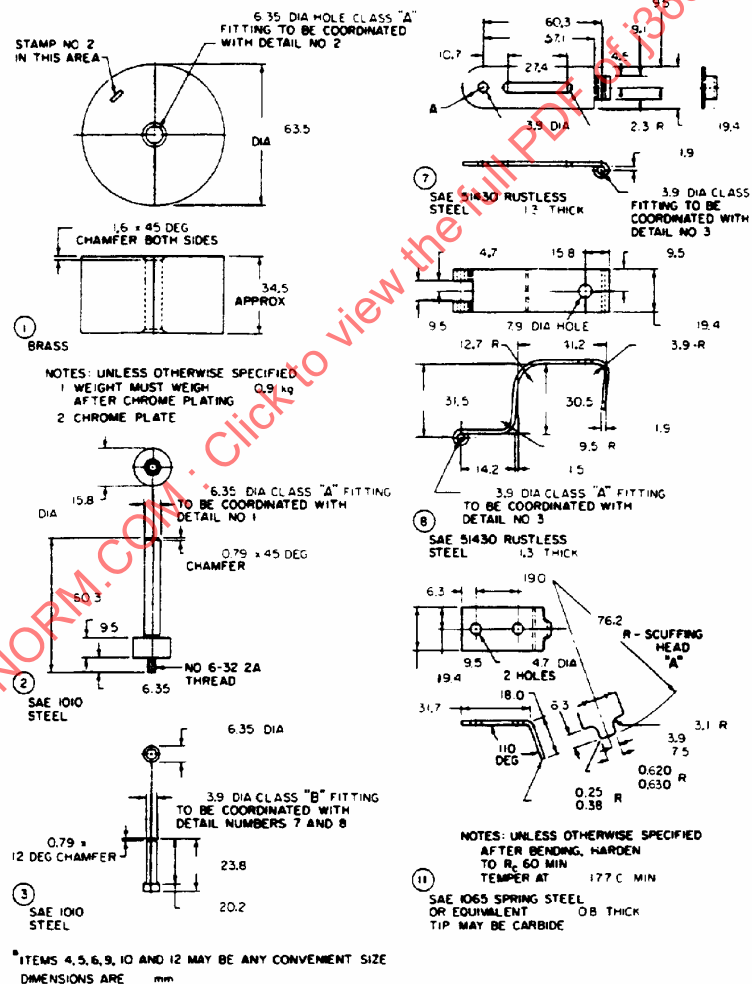


FIGURE 1—COMPONENTS OF SCUFFING ASSEMBLY

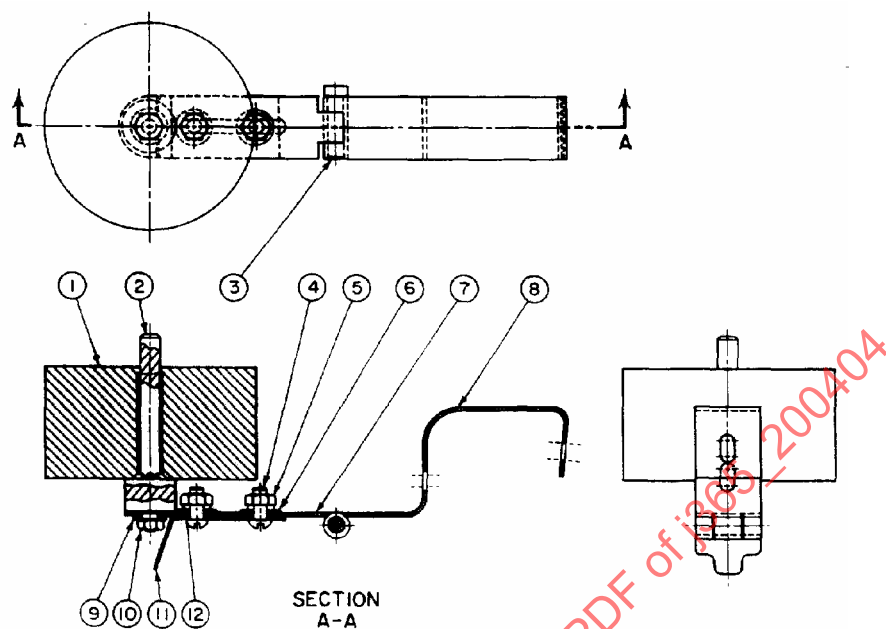


FIGURE 2—ASSEMBLY OF SCUFFING TEST FIXTURE  
(SEE FIGURE 1 FOR EXPLANATION OF NUMBERS)

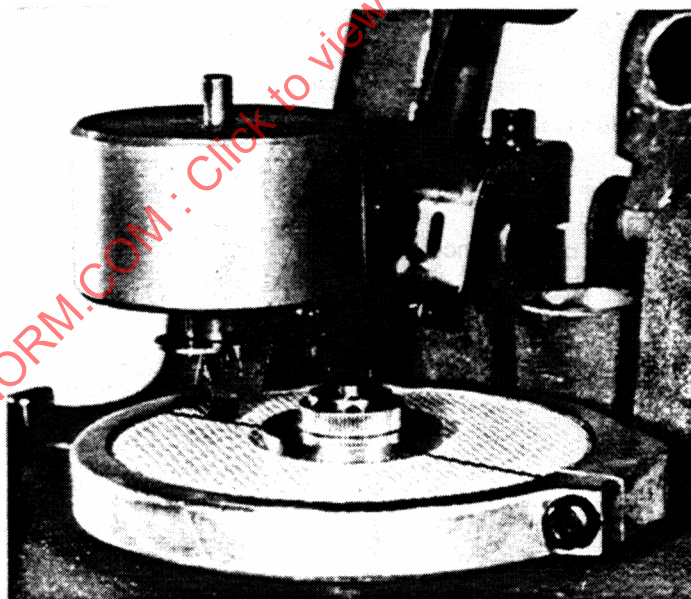


FIGURE 3—ATTACHMENT OF SCUFFING TEST FIXTURE TO ABRADER

#### **4. Procedure**

##### **4.1 Conditioning**

The test specimens shall be conditioned for a minimum of 24 h at 21 °C  $\pm$  2 °C and 50%  $\pm$  5% relative humidity for this test. Unless otherwise specified, the test shall be conducted under the same controlled conditions since a change in relative humidity and temperature can affect test results.

##### **4.2 Test Samples for Textiles, Coated Fabrics, Leather, or Similar Flexible Materials**

- a. Cut a 6.4 mm hole in the center of a 131 mm diameter specimen.
- b. Place the specimen on the rubber pad of the specimen holder.
- c. Place a 54 mm OD clamp plate over the material and tighten down securely with the clamping nut.
- d. Press the hold-down ring over the test specimen so that the material is drawn taut over the specimen holder with no wrinkles or bulges.
- e. Tighten the adjusting screw of the hold-down ring just enough to hold the test specimen but not so tight as to cause wrinkling or bulging.
- f. Place the assembled test specimen on the abrading machine and lower the scuff fixture onto the test specimen as shown in Figure 3.
- g. Scuff for the number of cycles indicated by the engineering specification.

##### **4.3 Test Samples for Fiberboard, Rubber Floor Mats, Carpets, and Other Semirigid Materials**

- a. Cut a 6.4 mm hole in the center of a 106 mm diameter test specimen.
- b. Place the test specimen on the rubber pad on the specimen holder and tighten down securely with a 32 mm clamp plate and nut.
- c. Place the hold-down ring over the test specimen, press the ring with the fingers, and tighten it. The specimen, when properly secured, shall be free of wrinkles and bulges.
- d. Place the assembled test specimen on the abrading machine and lower the scuff fixture onto the test specimen as shown in Figure 3.
- e. Scuff the test specimen for the number of cycles indicated by the engineering specification.

#### **5. Reporting**

Observe and report scuff resistance by comparing the test specimen to an approved master scuff specimen and mounting configuration established by the customer. Report configuration tested.

#### **6. Notes**

##### **6.1 Marginal Indicia**

The (R) is for the convenience of the user in locating areas where technical revisions have been made to the previous issue of the report. If the symbol is next to the report title, it indicates a complete revision of the report.

PREPARED BY THE SAE TEXTILES AND FLEXIBLE PLASTICS COMMITTEE